



ELSEVIER

# Material strategies for creating artificial cell-instructive niches

Faramarz Edalat<sup>1,2</sup>, Iris Sheu<sup>1,2,3</sup>, Sam Manoucheri<sup>1,2</sup> and Ali Khademhosseini<sup>1,2,4</sup>

There has been a tremendous growth in the use of biomaterials serving as cellular scaffolds for tissue engineering applications. Recently, advanced material strategies have been developed to incorporate structural, mechanical, and biochemical signals that can interact with the cell and the *in vivo* environment in a biologically specific manner. In this article, strategies such as the use of composite materials and material processing methods to better mimic the extracellular matrix, integration of mechanical and topographical properties of materials in scaffold design, and incorporation of biochemical cues such as cytokines in tethered, soluble, or time-released forms are presented. Finally, replication of the dynamic forces and biochemical gradients of the *in vivo* cellular environment through the use of microfluidics is highlighted.

## Addresses

<sup>1</sup> Center for Biomedical Engineering, Department of Medicine, Brigham and Women's Hospital, Harvard Medical School, Cambridge, MA 02139, USA

<sup>2</sup> Harvard-MIT Division of Health Sciences and Technology, Massachusetts Institute of Technology, Cambridge, MA 02139, USA

<sup>3</sup> Department of Biological Engineering, Massachusetts Institute of Technology, Cambridge, MA 02139, USA

<sup>4</sup> Wyss Institute for Biologically Inspired Engineering, Harvard University, Boston, MA 02115, USA

Corresponding author: Khademhosseini, Ali ([alik@rics.bwh.harvard.edu](mailto:alik@rics.bwh.harvard.edu))

Current Opinion in Biotechnology 2012, 23:820–825

This review comes from a themed issue on **Tissue, cell and pathway engineering**

Edited by **Hal Alper** and **Wilfried Weber**

For a complete overview see the [Issue](#) and the [Editorial](#)

Available online 15th June 2012

0958-1669/\$ – see front matter, © 2012 Elsevier Ltd. All rights reserved.

<http://dx.doi.org/10.1016/j.copbio.2012.05.007>

## Introduction

In the engineering of tissues, a scaffold is often required to provide an environment or *niche* that favors the natural behavior of cells. This scaffold must fulfill a wide range of requirements, from physical and biochemical to cellular parameters [1,2]. These requirements have stemmed from the notion that mimicking the extracellular environment—its structure, mechanical and biochemical properties—in designing cellular scaffolds, will coax cells to behave in the same manner as their *in vivo* counterparts. Engineering of such scaffolds requires close attentiveness to several material design criteria: (i) the 3-dimensional


(3D) micro-geometry within the scaffold including porosity, pore size, and interpore connectivity to satisfy adequate mass transfer of gases, nutrients, and waste as well as cell attachment and spreading, and tissue formation; (ii) mechanical parameters such as linearity or non-linearity, elasticity, viscoelasticity, or anisotropy that must be tailored to the specific tissue in mind; and (iii) successful delivery of biologics including cells, nucleic acids, and cytokines. In this review, these three material design criteria will be discussed, methods utilized to mimic the *in vivo* cell microenvironment will be highlighted, and recent research contributing to better bioactive scaffold fabrication using advanced material strategies will be presented (Figure 1). Such materials can either directly alter the cellular differentiation pathways or be used as permissive environments for approaches in which the cell phenotype is altered using ‘pathway engineering’ approaches. An example of the latter approach is to develop advanced materials that enable the generation of induced pluripotent stem cells [3].

## Creating the cellular scaffold

In choosing the material to be used for a scaffold, a wide range of options exists—natural and synthetic materials, and composites of two or more from the same class or different classes of materials; the advantages and disadvantages of using that material must be known, in addition to its suitability for the desired application. Naturally-derived materials are often purified extracellular matrix (ECM) proteins (collagen, gelatin [4], laminin, hyaluronic acid) or a mixture (Matrigel<sup>®</sup>). Other sources may be from plant and animal constituents (silk, agarose, chitosan). Alternatively, decellularized organs that retain the ECM and architecture of tissues have been used to engineer blood vessel [5], heart [6], lung [7<sup>•</sup>], liver [8], and bone [9]. The advantages of natural materials are their biological activity and biocompatibility. Synthetic materials, on the contrary, overcome the disadvantages posed by their natural counterparts—mainly, their manufacturing and processing variability and inability to control their physico-chemical properties. Additionally, synthetic materials provide a blank slate with absence of biological activity that may be modified through biochemical means (discussed in ‘Biochemical modulation of materials’ section) [10].

More often than expected, single-component materials do not meet the requirements needed for a cellular scaffold. For instance, they may lack the desired mechanical properties, electrical activity, or cell–matrix interactions. Composite

Figure 1

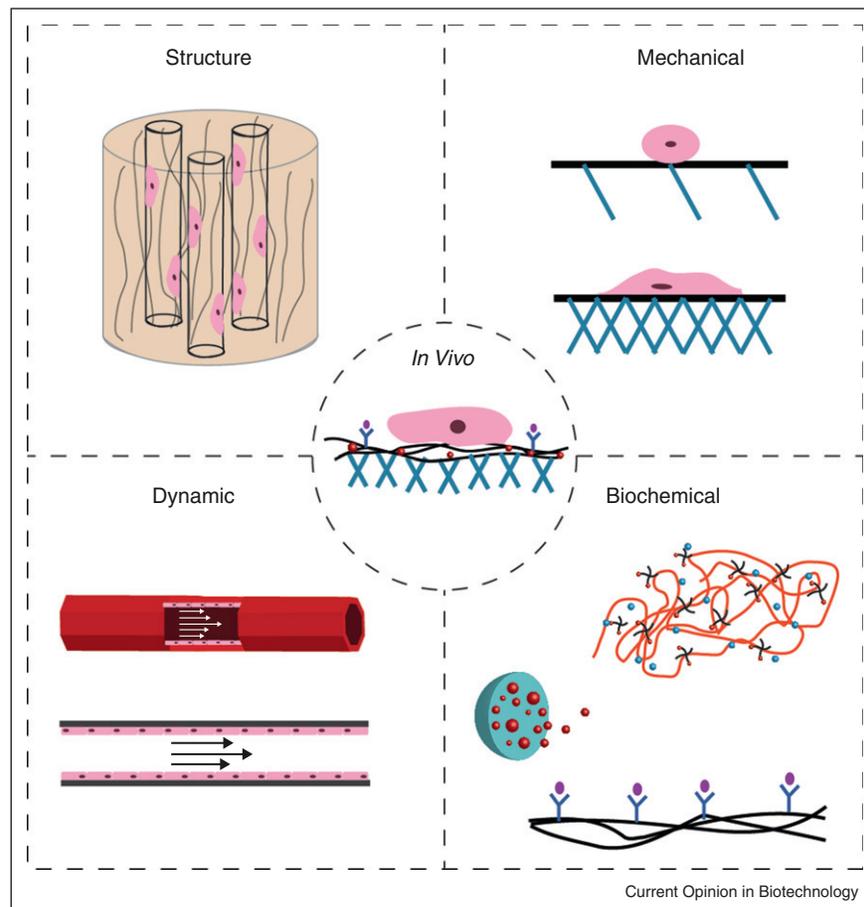

Schematic representation of the material strategies (structural, mechanical, biochemical, and dynamic) utilized to encode tissue-engineering scaffolds with biological information to mimic the *in vivo* cellular microenvironment.

materials may be used to overcome these limitations. While mixing materials from the same class [11] will provide a degree of modulation, combining materials from different classes will generate a greater measure of control over its properties. For instance, bone is composed of collagen (a polymer) and hydroxyapatite nanocrystals (a ceramic); hence, polymer/ceramic composites have been widely used in bone tissue engineering [12]. Hydrogels are another case in point; they are a cross-linked network of monomers, oligomers, or polymers that contain 90–95% water in volume and structurally resemble the ECM [13]. However, they often lack the mechanical strength needed for certain tissue engineering applications. In a work by Shin *et al.*, gelatin methacrylate hydrogels, which favor cell attachment and spreading but lack strong mechanical properties were reinforced with carbon nanotubes, which resulted in a composite with increased compressive modulus, while material pore size and cell adhesiveness remained the same [14<sup>•</sup>]. Furthermore, carbon nanotube-based composites have been used to direct differentiation of mesenchymal stem cells toward the osteogenic

lineage [15], increase connexin 43 expression of cardiac constructs [16], and enhance the electrical activity of neural tissues [17<sup>••</sup>], given the electrical conduction properties of carbon nanotubes.

In designing a scaffold, it is ideal that the scaffold, over an intended period of time, should degrade and be replaced with naturally deposited ECM and the newly formed tissue. In this regard, linear aliphatic polyesters such as poly(lactic acid) and poly(glycolic acid) have been routinely used owing to their biodegradability—given the susceptibility of their ester bonds to hydrolysis—and ability to fine-tune their degradation rate. Alternatively, non-biodegradable materials, such as poly(ethylene glycol) (PEG), can be incorporated with matrix metalloproteinase (MMP)-sensitive peptides to make them physiologically degradable. The addition of such peptides has been shown to directly affect gene expression, as shown by the increased maturation of cardioprogenitors via increase in myosin heavy chain-positive cells when grown on MMP-sensitive gels [18].

Another important consideration in cellular scaffold fabrication is scaffold structure. In the past, emphasis was placed on macroporous structures to facilitate mass transfer of vital molecules. These scaffolds were often fabricated with microspheres, salt leaches, or gas foams [19]. However, the micron-scale dimensions of these material structures do not recapitulate the nanometer-scale, fibrillar aspect of the structure of ECM. To generate these nanofibers, techniques such as electrospinning [20], molecular self-assembly [21,22], and phase separation [23] have been employed. Hydrogels, discussed previously, are a class of materials that have proven to be particularly biomimetic and is now widely used in the biological and medical fields [24].

### Mimicking the physical aspects of the cell's microenvironment

The physical aspects of the cell's microenvironment can be broken down into substrate mechanics and surface topography. Depending on their anatomical location, tissues have a wide range of mechanical properties. For instance, the elastic moduli of brain (0.5 kPa) is relatively soft compared to muscles and skin (about 10 kPa) and precalcified bone (>30 kPa) [25]. Another challenge in recreating the native cellular environment is that many tissues are viscoelastic with non-linear, anisotropic, and heterogeneous mechanical properties [1]. Cellular scaffolds used for the repair or replacement of diseased tissues must have adequate mechanical integrity to withstand physiological loading, as in the case of engineered blood vessel, heart, bone, and cartilage constructs. Hence, in designing a material, the mechanical properties of the tissue that the material will replace should be carefully considered, and ideally the two should match. The effects of substrate stiffness on cell cytoskeletal remodeling, cell proliferation, and stem cell differentiation [26,27] are well known [28]. For instance, fibroblast, endothelial and epithelial cell growth is enhanced on stiffer substrates, whereas neurons prefer softer substrates [29]. Employing this knowledge, Gilbert *et al.* showed that the skeletal muscle stem cells grown *in vitro* on laminin-coated PEG with elasticity similar to that of muscle had enhanced self-renewal, as assessed via myogenin transcription factor expression, and increased *in vivo* regenerative capacity when subsequently transplanted in mice [30]. Common methods of altering the Young's modulus of polymeric materials have involved varying the precursor molecular weight or concentration, or the chemistry or degree of cross-linking. However, this often leads to a simultaneous change in the binding sites of the material and the two parameters cannot be independently assessed. While new chemistry approaches, such as Diels–Alder [31] or Huisgen [32] cycloadditions, have overcome these obstacles, there is often a compromise between the mechanical strength of a material and its porous nature. In this regard, composite materials have overcome these disadvantages with the use of nanoscale fibers (e.g. non-woven, woven,

or knitted polymers), tubes (e.g. carbon nanotubes) [33], wires and belts (e.g. nanotitanates) [34], or particulates (e.g. gold or silicate) [35] to modulate the bulk mechanical properties of materials. For instance, in work by Moutos *et al.*, 3D woven poly(glycolic acid) structures were generated as reinforcing agents in agarose and fibrin hydrogels that reproduced the viscoelasticity, tension-compression non-linearity, and anisotropy of native cartilage tissue, and maintained the rounded phenotype of chondrocytes [36].

Another important physical parameter in the cell's microenvironment is surface topography. The ECM, through its 3D structure, presents topographical cues that influences cell processes such as cell adhesion, morphology, migration, and differentiation. Microfabrication and nanofabrication technologies such as photolithography, soft lithography, and electron beam lithography have been widely used to create topographies such as grooves, pillars, and lattices, among other shapes. These topographies are often used to create anisotropic cell and tissue constructs or direct specific cellular processes [37] such as neurite extension. In many tissue types (e.g. myocardium, bone, and cartilage), the anisotropy of cells and tissues is intricately connected with the function of that tissue. Hence, fabrication of topographically containing biomaterials has been used in various tissue-engineering applications. For instance, microfluidic-generated grooved alginate microfibers were shown to produce a greater degree of neurite extension and orientation compared to smooth microfibers [38]. Finally, the fabrication of a poly(glycerol-sebacate) scaffold with an accordion-shaped honeycomb structure resulted in anisotropic and tensile mechanical properties similar to that of the ventricular myocardium, and resulted in directionally dependent electrical excitation thresholds [39]. While the use of fabricated topography has provided insight into various cellular processes, future work must be directed into uncovering the mechanism behind such effects.

### Biochemical modulation of materials

To generate cell-instructive scaffolds, it is necessary to encode them with biological information. *In vivo*, this information is in the form of signaling molecules or cytokines, in tethered or freely soluble forms. Currently, the material strategies for presenting cytokines within scaffolds include covalent attachment, adsorption, and use of controlled-release particles [40]. One of the initial steps after seeding cells on or into a scaffold is integrin-mediated cell attachment. Hence, covalent attachment of arginine-glycine-aspartate (RGD) sequences, a ligand for integrins, to inert synthetic materials such as PEG or polysaccharides such as hyaluronic acid is a common method to promote cell adhesion. Covalent attachment of these peptides and also protein fragments or full length proteins are possible through targeting the thiol, amino, or carboxylic groups of these molecules [41]. While covalent

conjugation presents a method that prevents the diffusion of cytokines out of the scaffold, it is an atypical mode of molecular presentation. *In vivo*, growth factors and other types of signaling molecules are often ECM-bound, through non-covalent interactions with glycosaminoglycans (GAGs) including heparin, heparin-sulfate and chondroitin-sulfate. The interaction of GAGs with growth factors involves their sequestration, protection from hydrolytic enzymes, and presentation to cell surface receptors. Therefore, the incorporation of GAGs in scaffolds have been employed as a method of presenting and delivering growth factors [42]. While tethering does simulate the presentation of some cytokines [43], many other cytokines are secreted by cells in soluble form for intercellular communication. Hence, drug release strategies have been employed in tissue engineered scaffolds to have control over the temporal kinetics of signaling molecules. These include cytokine encapsulation within porous scaffolds for burst release, microparticulates and nanoparticulates [44] synthesized through double emulsion techniques for sustained or delayed release [45], and on demand release through the use of stimuli-responsive polymers [46]. For instance, fibroblast growth factor-2 (FGF-2)-containing polyvalent coacervates were used for the controlled subcutaneous delivery of FGF-2 and resulted in enhanced angiogenesis as demonstrated by increased recruitment of endothelial and mural cells and maturation of blood vessels [47]. The successes of these drug release strategies are evident from their widespread use in current clinical trials and therapeutics.

Another aspect of biomaterial chemical modification that deserves to be mentioned is surface chemistry. The chemical moieties present at the surface of biomaterials are critical for cellular functions such as cell adhesion, migration, proliferation, and differentiation [48]. In addition, the surface of biomaterials plays a key role in the integration of tissue engineered constructs and implants. Using a surface chemistry approach, Wang *et al.* functionalized the surface of chondroitin sulfate scaffold with an adhesive containing methacrylate and aldehyde groups that promoted tissue integration via the formation of covalent bonds with the scaffold (through polymerization reaction) and native cartilage, respectively [49].

### Moving from static to dynamic environments

In the *in vivo* microenvironment, a dynamic interplay exists between cells and biochemical and physical cues that currently cannot be controlled in standard *in vitro* models. Microfluidics, a field involving the manipulation of fluids at the micron-scale dimension, has made it possible to replicate the dynamic *in vivo* conditions in *in vitro* models [50,51]. Commonly used materials in microfluidic devices include poly(dimethylsiloxane) or polyesters that may be undesirable given their non-degradability or lack of robust mechanical properties

[52]. One solution has been through the use of silk fibroin, amenable to soft lithographic methods, to fabricate biocompatible and biodegradable microfluidic devices with high mechanical modulus and toughness [53].

An advantage central to using microfluidic devices in tissue engineering is the ability to control the mechanical properties of the cell's microenvironment [54]. One way that this is achieved is through mimicking the stress and shear forces present *in vivo* such as those produced by blood flow [55], heart contractions, and lung movements. For instance, engineered human microvessels exposed to high flow resulted in vascular barrier functions that rivaled those of *in vivo* conditions [56]. In another work, replication of cyclical mechanical stimulation of cardiac tissues was accomplished with a pulsatile pressure-actuated microfluidic device that induced the preload and afterload effects on embryonic cardiomyoblasts and resulted in the establishment of an *in vivo* phenotype [57]. Lastly, the breathing movement of the lungs was replicated by a vacuum-assisted microfluidic device, cyclically applying mechanical strain to an alveolar-capillary interface that reproduced pulmonary inflammation responses [58].

Microfluidics also allows for precise control over the chemistry and geometry of the environment. Methods to control cytokine concentration gradients [59], important in embryonic development and tissue formation [60] have been developed. For instance, Choi *et al.* developed a dual hydrogel membrane within microchannels to produce stable concentration gradients that could be applied to chemotaxis studies [61]. Geometric control can be achieved through adjusting channel dimensions or employing a layer-by-layer approach. In addition, recently, self-assembling microfluidic devices with curved patterns have been developed [62].

Disadvantages to incorporating microfluidics with tissue engineering include small sample sizes and methods that are not yet fully developed or scalable. However, the ability for microfluidics to generate mechanical, chemical, and geometric constraints similar to those found in physiological conditions are unparalleled by current methods, thus rendering it valuable to the field of tissue engineering as demonstrated by microfabricated models of brain, blood vessels, skeletal muscles, heart, lung, liver, intestines [63], liver, and tumors [64].

### Future outlooks

Advanced material strategies stemming from materials science, physics, chemistry, and biology have heralded a new era in the design of tissue engineering scaffolds whereby the biochemical, mechanical, and structural details of a cell's microenvironment or *niche* can be replicated to influence cell behaviors such as gene expression, adhesion, migration, and differentiation. However,

more work needs to be done to understand the properties of native tissues, to define proper mechanical characterization of biomaterials, and to determine the mechanisms behind the regenerative processes that are necessary for a successful tissue replacement. Furthermore, a topic of importance not discussed here is the biomaterials' interaction with the body's immune system, which will also dictate how well an engineered implant can be integrated within host tissue. Overall, the materials-driven tissue-engineering discoveries discussed hold great promises in the near future for the replacement of damaged or diseased tissues.

## Acknowledgements

The authors acknowledge funding from the National Science Foundation CAREER Award (DMR 0847287), the office of Naval Research Young National Investigator Award, and the National Institutes of Health (HL092836, DE019024, EB012597, AR057837, DE021468, HL099073, EB008392).

## References and recommended reading

Papers of particular interest, published within the period of review, have been highlighted as:

- of special interest
- of outstanding interest

1. Hollister SJ: **Scaffold design and manufacturing: from concept to clinic.** *Adv Mater* 2009, **21**:3330-3342.
2. Edalat F, Bae H, Manoucheri S, Cha JM, Khademhosseini A: **Engineering approaches toward deconstructing and controlling the stem cell environment.** *Ann Biomed Eng* 2012, **40**:1301-1315.
3. Ye JH, Xu YJ, Gao J, Yan SG, Zhao J, Tu Q, Zhang J, Duan XJ, Sommer CA, Mostoslavsky G *et al.*: **Critical-size calvarial bone defects healing in a mouse model with silk scaffolds and SATB2-modified iPSCs.** *Biomaterials* 2011, **32**:5065-5076.
4. Chen Y-C, Lin R-Z, Qi H, Yang Y, Bae H, Melero-Martin JM, Khademhosseini A: **Functional human vascular network generated in photocrosslinkable gelatin methacrylate hydrogels.** *Adv Funct Mater* 2012 <http://dx.doi.org/10.1002/adfm.201101662>.
5. Quint C, Kondo Y, Manson RJ, Lawson JH, Dardik A, Niklason LE: **Decellularized tissue-engineered blood vessel as an arterial conduit.** *Proc Natl Acad Sci USA* 2011, **108**:9214-9219.
6. Ott HC, Matthiesen TS, Goh S-K, Black LD, Kren SM, Netoff TI, Taylor DA: **Perfusion-decellularized matrix: using nature's platform to engineer a bioartificial heart.** *Nat Med* 2008, **14**:213-221.
7. Petersen TH, Calle EA, Zhao L, Lee EJ, Gui L, Raredon MB, Gavrilov K, Yi T, Zhuang ZW, Breuer C *et al.*: **Tissue-engineered lungs for in vivo implantation.** *Science* 2010, **329**:538-541.  
Tissue-engineered lungs were generated by seeding pulmonary epithelial and endothelial cells onto decellularized adult rat lungs, and demonstrated similar hierarchical organization and mechanical characteristics as that of native lung tissue.
8. Uygun BE, Soto-Gutierrez A, Yagi H, Izamis M-L, Guzzardi MA, Shulman C, Milwid J, Kobayashi N, Tilles A, Berthiaume F *et al.*: **Organ reengineering through development of a transplantable recellularized liver graft using decellularized liver matrix.** *Nat Med* 2010, **16**:814-820.
9. Grayson WL, Frohlich M, Yeager K, Bhumiratana S, Chan ME, Cannizzaro C, Wan LQ, Liu XS, Guo XE, Vunjak-Novakovic G: **Engineering anatomically shaped human bone grafts.** *Proc Natl Acad Sci USA* 2010, **107**:3299-3304.
10. Zhu J: **Bioactive modification of poly(ethylene glycol) hydrogels for tissue engineering.** *Biomaterials* 2010, **31**:4639-4656.
11. Shin H, Olsen BD, Khademhosseini A: **The mechanical properties and cytotoxicity of cell-laden double-network hydrogels based on photocrosslinkable gelatin and gellan gum biomacromolecules.** *Biomaterials* 2012, **33**:3143-3152.
12. Zhang P, Hong Z, Yu T, Chen X, Jing X: **In vivo mineralization and osteogenesis of nanocomposite scaffold of poly(lactide-co-glycolide) and hydroxyapatite surface-grafted with poly(L-lactide).** *Biomaterials* 2009, **30**:58-70.
13. Tibbitt MW, Anseth KS: **Hydrogels as extracellular matrix mimics for 3D cell culture.** *Biotechnol Bioeng* 2009, **103**:655-663.
14. Shin SR, Bae H, Cha JM, Mun JY, Chen YC, Tekin H, Shin H, Farshchi S, Dokmeci MR, Tang S *et al.*: **Carbon nanotube reinforced hybrid microgels as scaffold materials for cell encapsulation.** *ACS Nano* 2012, **6**:362-372.  
Gelatin methacrylate hydrogels were re-inforced with carbon nanotubes to increase mechanical strength of scaffolds, while retaining pore size and cell adhesiveness.
15. Namgung S, Baik KY, Park J, Hong S: **Controlling the growth and differentiation of human mesenchymal stem cells by the arrangement of individual carbon nanotubes.** *ACS Nano* 2011, **5**:7383-7390 <http://dx.doi.org/10.1021/nn2023057>.
16. You JO, Rafat M, Ye GJ, Auguste DT: **Nanoengineering the heart: conductive scaffolds enhance connexin 43 expression.** *Nano Lett* 2011, **11**:3643-3648.
17. Cellot G, Cilia E, Cipollone S, Rancic V, Sucapane A, Giordani S, Gambazzi L, Markram H, Grandolfo M, Scaini D *et al.*: **Carbon nanotubes might improve neuronal performance by favouring electrical shortcuts.** *Nat Nanotechnol* 2009, **4**:126-133.  
Provides a mechanism on how carbon nanotubes enhance the electrical activities of neurons *in vitro*.
18. Kraehenbuehl TP, Zammaretti P, Van der Vlies AJ, Schoenmakers RG, Lutolf MP, Jaconi ME, Hubbell JA: **Three-dimensional extracellular matrix-directed cardioprogenitor differentiation: systematic modulation of a synthetic cell-responsive PEG-hydrogel.** *Biomaterials* 2008, **29**:2757-2766.
19. Annabi N, Mithieux SM, Boughton EA, Ruys AJ, Weiss AS, Dehghani F: **Synthesis of highly porous crosslinked elastin hydrogels and their interaction with fibroblasts in vitro.** *Biomaterials* 2009, **30**:4550-4557.
20. Sill TJ, von Recum HA: **Electrospinning: applications in drug delivery and tissue engineering.** *Biomaterials* 2008, **29**:1989-2006.
21. Hartgerink JD, Beniash E, Stupp SI: **Self-assembly and mineralization of peptide-amphiphile nanofibers.** *Science* 2001, **294**:1684-1688.
22. Cui H, Webber MJ, Stupp SI: **Self-assembly of peptide amphiphiles: from molecules to nanostructures to biomaterials.** *Biopolymers* 2010, **94**:1-18.
23. Liu X, Ma PX: **Phase separation, pore structure, and properties of nanofibrous gelatin scaffolds.** *Biomaterials* 2009, **30**:4094-4103.
24. Slaughter BV, Khurshid SS, Fisher OZ, Khademhosseini A, Peppas NA: **Hydrogels in regenerative medicine.** *Adv Mater* 2009, **21**:3307-3329.
25. Nemir S, West JL: **Synthetic materials in the study of cell response to substrate rigidity.** *Ann Biomed Eng* 2010, **38**:2-20.
26. Huebsch N, Arany PR, Mao AS, Shvartsman D, Ali OA, Bencherif SA, Rivera-Feliciano J, Mooney DJ: **Harnessing traction-mediated manipulation of the cell/matrix interface to control stem-cell fate.** *Nat Mater* 2010, **9**:518-526.
27. Holst J, Watson S, Lord MS, Eamegdool SS, Bax DV, Nivison-Smith LB, Kondyurin A, Ma L, Oberhauser AF, Weiss AS *et al.*: **Substrate elasticity provides mechanical signals for the expansion of hemopoietic stem and progenitor cells.** *Nat Biotechnol* 2010, **28**:1123-1128.  
Investigates the role of substrate elasticity on hemopoietic stem cells by showing enhancement of cell expansion on tropoelastin substrates.
28. Discher DE, Janmey P, Wang Y-I: **Tissue cells feel and respond to the stiffness of their substrate.** *Science* 2005, **310**:1139-1143.

29. Engler AJ, Griffin MA, Sen S, Bonnemann CG, Sweeney HL, Discher DE: **Myotubes differentiate optimally on substrates with tissue-like stiffness: pathological implications for soft or stiff microenvironments.** *J Cell Biol* 2004, **166**:877-887.
30. Gilbert PM, Havenstrite KL, Magnusson KE, Sacco A, Leonardi NA, Kraft P, Nguyen NK, Thrun S, Lutolf MP, Blau HM: **Substrate elasticity regulates skeletal muscle stem cell self-renewal in culture.** *Science* 2010, **329**:1078-1081.
31. Kolb HC, Finn MG, Sharpless KB: **Click chemistry: diverse chemical function from a few good reactions.** *Angew Chem Int Ed Engl* 2001, **40**:2004-2021.
32. Nandivada H, Chen H-Y, Bondarenko L, Lahann J: **Reactive polymer coatings that "click".** *Angew Chem Int Ed Engl* 2006, **45**:3360-3363.
33. Lewitus DY, Landers J, Branch J, Smith KL, Callegari G, Kohn J, Neimark AV: **Biohybrid carbon nanotube/agarose fibers for neural tissue engineering.** *Adv Funct Mater* 2011, **21**:2624-2632.
34. Wu S, Liu X, Hu T, Chu PK, Ho JP, Chan YL, Yeung KW, Chu CL, Hung TF, Huo KF et al.: **A biomimetic hierarchical scaffold: natural growth of nanotitanates on three-dimensional microporous Ti-based metals.** *Nano Lett* 2008, **8**:3803-3808.
35. Choi SW, Zhang Y, Thomopoulos S, Xia Y: **In vitro mineralization by preosteoblasts in poly(DL-lactide-co-glycolide) inverse opal scaffolds reinforced with hydroxyapatite nanoparticles.** *Langmuir* 2010, **26**:12126-12131.
36. Moutos FT, Freed LE, Guilak F: **A biomimetic three-dimensional woven composite scaffold for functional tissue engineering of cartilage.** *Nat Mater* 2007, **6**:162-167.
37. Nikkhah M, Edalat F, Manoucheri S, Khademhosseini A: **Engineering microscale topographies to control the cell-substrate interface.** *Biomaterials* 2012, **33**:5230-5246.
38. Kang E, Jeong GS, Choi YY, Lee KH, Khademhosseini A, Lee S-H: **Digitally tunable physicochemical coding of material composition and topography in continuous microfibres.** *Nat Mater* 2011, **10**:877-883.
39. Engelmayr GC Jr, Cheng M, Bettinger CJ, Borenstein JT, Langer R, Freed LE: **Accordion-like honeycombs for tissue engineering of cardiac anisotropy.** *Nat Mater* 2008, **7**:1003-1010.
40. Chen FM, Zhang M, Wu ZF: **Toward delivery of multiple growth factors in tissue engineering.** *Biomaterials* 2010, **31**:6279-6308.
41. Jabbari E: **Bioconjugation of hydrogels for tissue engineering.** *Curr Opin Biotechnol* 2011, **22**:655-660.
42. Nie T, Baldwin A, Yamaguchi N, Kiick KL: **Production of heparin-functionalized hydrogels for the development of responsive and controlled growth factor delivery systems.** *J Control Release* 2007, **122**:287-296.
43. Tayalia P, Mooney DJ: **Controlled growth factor delivery for tissue engineering.** *Adv Mater* 2009, **21**:3269-3285.
44. Zhang S, Uludag H: **Nanoparticulate systems for growth factor delivery.** *Pharm Res* 2009, **26**:1561-1580.
45. Wang X, Wenk E, Zhang X, Meinel L, Vunjak-Novakovic G, Kaplan DL: **Growth factor gradients via microsphere delivery in biopolymer scaffolds for osteochondral tissue engineering.** *J Control Release* 2009, **134**:81-90.
- Evaluated the effects of multiple growth factor-loaded microsphere within a polymeric scaffold on mesenchymal stem cell osteochondral differentiation.
46. Zhao X, Kim J, Cezar CA, Huebsch N, Lee K, Bouhadir K, Mooney DJ: **Active scaffolds for on-demand drug and cell delivery.** *Proc Natl Acad Sci USA* 2011, **108**:67-72.
47. Chu H, Gao J, Chen CW, Huard J, Wang Y: **Injectable fibroblast growth factor-2 coacervate for persistent angiogenesis.** *Proc Natl Acad Sci USA* 2011, **108**:13444-13449.
48. Camci-Unal G, Nichol JW, Bae H, Tekin H, Bischoff J, Khademhosseini A: **Hydrogel surfaces to promote attachment and spreading of endothelial progenitor cells.** *J Tissue Eng Regen Med* 2012 <http://dx.doi.org/10.1002/term517>.
49. Wang DA, Varghese S, Sharma B, Strehin I, Fermanian S, Gorham J, Fairbrother DH, Cascio B, Elisseeff JH: **Multifunctional chondroitin sulphate for cartilage tissue-biomaterial integration.** *Nat Mater* 2007, **6**:385-392.
50. Sudo R, Chung S, Zervantonakis IK, Vickerman V, Toshimitsu Y, Griffith LG, Kamm RD: **Transport-mediated angiogenesis in 3D epithelial coculture.** *FASEB J* 2009, **23**:2155-2164.
51. Huang CP, Lu J, Seon H, Lee AP, Flanagan LA, Kim H-Y, Putnam AJ, Jeon NL: **Engineering microscale cellular niches for three-dimensional multicellular co-cultures.** *Lab Chip* 2009, **9**:1740-1748.
52. Chung BG, Lee KH, Khademhosseini A, Lee SH: **Microfluidic fabrication of microengineered hydrogels and their application in tissue engineering.** *Lab Chip* 2012, **12**:45-59.
53. Bettinger CJ, Cyr KM, Matsumoto A, Langer R, Borenstein JT, Kaplan DL: **Silk fibroin microfluidic devices.** *Adv Mater* 2007, **19**:2847-2850.
54. Freytes DO, Wan LQ, Vunjak-Novakovic G: **Geometry and force control of cell function.** *J Cell Biochem* 2009, **108**:1047-1058.
55. Lam RHW, Sun Y, Chen W, Fu J: **Elastomeric microposts integrated into microfluidics for flow-mediated endothelial mechanotransduction analysis.** *Lab Chip* 2012 <http://dx.doi.org/10.1039/C2LC21146G>.
56. Price GM, Wong KHK, Truslow JG, Leung AD, Acharya C, Tien J: **Effect of mechanical factors on the function of engineered human blood microvessels in microfluidic collagen gels.** *Biomaterials* 2010, **31**:6182-6189.
57. Giridharan GA, Nguyen MD, Estrada R, Parichehreh V, Hamid T, Ismahil MA, Prabhu SD, Sethu P: **Microfluidic cardiac cell culture model ( $\mu$ CCCM).** *Anal Chem* 2010, **82**:7581-7587.
58. Huh D, Matthews BD, Mammoto A, Montoya-Zavala M, Hsin HY, Ingber DE: **Reconstituting organ-level lung functions on a chip.** *Science* 2010, **328**:1662-1668.
- Develops a two-compartment microfluidic chip with seeded alveolar epithelial and endothelial cells to generate a lung-on-a-chip model that mimics the cyclical mechanical strain, and that can be used for diagnostic purposes.
59. Selimović S, Sim WY, Kim SB, Jang YH, Lee WG, Khabiry M, Bae H, Jambovane S, Hong JW, Khademhosseini A: **Generating nonlinear concentration gradients in microfluidic devices for cell studies.** *Anal Chem* 2011, **83**:2020-2028.
60. Nguyen EH, Schwartz MP, Murphy WL: **Biomimetic approaches to control soluble concentration gradients in biomaterials.** *Macromol Biosci* 2011, **11**:483-492.
61. Choi E, Jun I, Chang HK, Park KM, Shin H, Park KD, Park J: **Quantitatively controlled in situ formation of hydrogel membranes in microchannels for generation of stable chemical gradients.** *Lab Chip* 2012, **12**:302-308.
62. Jamal M, Zarafshar AM, Gracias DH: **Differentially photo-crosslinked polymers enable self-assembling microfluidics.** *Nat Commun* 2011, **2**:527 <http://dx.doi.org/10.1038/ncomms1531>.
63. Kim HJ, Huh D, Hamilton G, Ingber DE: **Human gut-on-a-chip inhabited by microbial flora that experiences intestinal peristalsis-like motions and flow.** *Lab Chip* 2012 <http://dx.doi.org/10.1039/C2LC40074J>.
64. Ghaemmaghami AM, Hancock MJ, Harrington H, Kaji H, Khademhosseini A: **Biomimetic tissues on a chip for drug discovery.** *Drug Discov Today* 2012, **17**:173-181.